

Optimization of Dyeing Variables for Simultaneous Extraction and Dyeing with Pure Natural Dye Obtained from Turmeric

Mamta Vashishtha

Amity School Of Fashion Technology, Amity University Rajasthan Kant Kalwar,
Nh 11-C, Delhi Jaipur Highway, Jaipur-303002
E-mail: mamtavashishtha@yahoo.com

Abstract—The present study was carried out at Department of Clothing and Textiles, Collage of Post Graduate Studies, G B Pant University of Agriculture and Technology, Pantnagar, Uttarakhand, India. Today the protection of environment has become a challenge for the chemical industries worldwide; All over the world the environment restrictions are becoming stricter. The need to realize the importance and the technology of natural dye is more urgent. The conventional aqueous extraction of natural dyes involves a time gap between extraction of dye and actual dyeing of the substrate. This exposure to time gap makes the dye dull and unappealing. The water soluble yellow dye from turmeric rhizomes (Curcumin) is very fugitive in nature. The hue becomes dull with exposure to time and temperature. To achieve the best dyeing results, a different method of dyeing was tried and tested, “Simultaneous extraction and dyeing” where dyeing of substrate is carried out in same water bath along with extraction of dye from the raw material. Observations proved that less temperature and reduced time of dyeing give better results in terms of colour appeal. Whereas analysis of the developed shades after a prolonged time gap of 23 years shows that the simultaneous extraction and dyeing produced more or less durable bright and appealing colours. As the colours are still appealing, even after a prolonged gap of 23 years. Thus turmeric dye obtained with this dyeing technique can be used as per the requirement of end product. A number of shades were developed with good to excellent washing fastness, through variations in dyeing conditions only. Results of numerous experiments reveal that same dye produced different shades under different dyeing conditions. Standard recipes have been developed for each shade. The final samples were tested for colour fastness to light and washing as per standards laid by Bureau of Indian standards at Indian Institute of Technology Delhi.

Keywords: Turmeric Rhizomes, curcumin, aqueous extraction of dye, Colorimetric tests, “Simultaneous extraction and dyeing”.

INTRODUCTION

The textile industry is one of the most pollutants releasing industries of the world. Pollutants released by the global textile industry are continuously doing unimaginable harm to the environment. Today the protection of environment has become a challenge for the chemical industries worldwide; All over the world the environment restrictions are becoming stricter. The need to realize the importance and the technology of natural dye is more urgent. This is then led to returning to traditional and more natural way of life (patel BH). Synthetic dyes are produced at high temperature and pressure from chemicals isolated from petroleum derivatives. During the manufacturing process of dyes many carcinogenic chemicals are used which leads to formation of toxic bi-products. These bi-products are discharged in the rivers, ponds or left in open. Hence cause severe atmospheric pollution (Paul R, 1996). This has threatened the ecological balance and called attention of the environmentalists to develop eco-friendly technologies to produce dyes from natural sources (Neelam Pruthi, 2007). The present study was aimed at developing 100% natural bright yellow colour for dyeing of wool without the use of any synthetic stuffs as mordants. A number of shades were developed with good to excellent washing fastness, through variations in dyeing conditions only. No synthetic chemical was used at any stage. Various studies have been carried out by different scientists on turmeric dye. However optimizing the dyeing conditions for turmeric dye, using simultaneous dyeing and extraction technique for dyeing of wool, investigated in the present study have not been reported earlier.

MATERIALS AND METHODS

Collection of Raw materials and their preparation:

Plant materials: Common name: Turmeric, Botanical name: Curcuma Longa, Family: ginger family, **Zingiberaceae**. It is native to southern Asia, requiring temperatures between 20 and 30 °C (68 and 86 °F) and a considerable amount of annual rainfall to

thrive. Part used: Rhizomes. (When not used fresh the rhizomes are boiled for about 30–45 minutes and then dried in hot ovens after which it is ready for sale in market for further use as a colouring agent for food and dyes.) Dried Turmeric Rhizomes were collected from the local market complex in G. B. Pant University campus, Pantnagar, Udham Singh nagar, Uttarakhand. Rhizomes were dried in shade and pulverized in a powder form in Wiley mill installed in the department of Post Harvest Technology, College of Technology, Pantnagar.

Instruments:

- Wiley mill was used for pulverizing the Turmeric Rhizomes.
- Optical density of dye solutions was measured by Spectrophotometer- G5866C
- Electronic balance was used for weighing the dye materials and wool.
- Water bath with thermostatic temperature control was used for dyeing the wool samples in glass beakers under controlled conditions.
- Mercury Bulb Tungston fluorescent lamp (MBTF) Light fastness Tester installed at the department of Textile Technology, IIT Delhi was used to test the colour fastness of dyed samples to light.
- Atlas Launder'ometer installed in the department of Textile Technology, IIT Delhi was used for testing washing fastness of dyed samples.

Wool: White Australian Merino wool was purchased from Shree Gandhi Ashram, Haldwani, Uttarakhand .

Blue Wool standards: Blue Wool standards were used (for fading along with samples) for testing colour fastness to light .

Grey Scale: Colour fastness rating was done with Grey Scale for evaluating changes in colour and staining as per ISO recommendations (ISO 105-A02: 1993 and ISO 105-A-03)

Processing of wool: The scouring of wool was done according to procedure mentioned by Hover 1976. Washed skeins of wool were allowed to dry and finally weighed for further experimentation.

Optimization of different variables: A series of experiments were conducted in order to standardize the different variables; such as dyeing technique, concentration of the dye material , time for extraction of dye, time for dyeing, temperature for extraction and temperature for dyeing. For dyeing of samples the MLR (material liquor ratio) selected was 1:10. The Optical density (OD) values of the dye solutions before and after dyeing were recorded. A sample of one ml was taken from each beaker and optical density was recorded by diluting it 20 times. The percent absorption was calculated by the following formula:

$$\% \text{ Absorption} = \frac{\text{OD before dyeing} - \text{OD after dyeing}}{\text{OD before dyeing}} \times 100$$

Dyed samples were judged by a panel of 15 judges visually on the criteria of luster, evenness of dye, depth of shade and overall appearance. From the total marks obtained the percentage ratings were calculated. Each optimized variable was used in further experiments where ever desired. The final range of shades was tested for colour fastness to light and washing as per standards laid by Bureau of Indian standards at the Department of Textile Technology, IIT Delhi.

Dyeing Techniques;

Dyeing Technique I (Simultaneous extraction & dyeing): Turmeric powder was tied in muslin bags (2 inch X 2 inch) with a thread to hold it. Pre soaked and weighed wool sample, and dye bag were put in a beaker containing 100 ml water. Beaker was placed in a boiling water bath (100⁰c). Simultaneous extraction and dyeing was carried out in glass beakers for one hour. Samples were stirred and dye bags were pounded with a glass rod after every five minutes to ensure even dyeing and continuous extraction of dye from muslin bag. After one hour dye bags were taken out and dyed samples were allowed to cool in dye bath itself. Then the samples were rinsed under running water and dried in shade.

Dyeing Technique II (Dyeing after extraction): In this technique the conventional method of dyeing has been used. The dye was extracted for one hour in a boiling water bath (100⁰c). The solution was then cooled and filtered. Pre soaked wool sample of 10 g was added to this dye solution and dyeing was carried out at 80⁰c for one hour. The samples were stirred with glass rod after every 10 minutes in order to obtain an even dyeing on sample. After one hour beakers were taken out of water bath and samples were allowed to cool in dye bath itself. Dyed samples were then rinsed under tap water and dried in shade. According to results obtained Technique I was selected for Turmeric dye. For further experiments Technique I was used.

Concentration of dye material: For optimization of concentration of Turmeric dye, 3 different concentrations i.e. 1g, 2g, & 3g were tested, Simultaneous extraction and dyeing was carried out for one hour at 100⁰c. The remaining process was repeated as explained earlier. Optical density was measured for all six solutions and dyed samples were evaluated by judges.

Time for simultaneous extraction & dyeing: Simultaneous extraction and dyeing was carried out with optimized concentration, for three different time durations i.e. 60, 120, 180 minutes respectively at 100⁰c. Rest of the procedure was done as mentioned earlier. Optical density was measured for all six solutions and dyed samples were evaluated by judges.

Temperature for simultaneous extraction & dyeing: Simultaneous extraction and Dyeing was carried out with optimum concentration of dye for optimized time duration at four different temperatures i.e. 40⁰c, 60⁰c, 80⁰c, 100⁰c. Optical density was measured for all eight solutions and dyed samples were evaluated by judges.

Preparation of Final samples: Final samples were prepared by dyeing the presoaked weighed wool sample with Turmeric using all optimized variables i.e. optimized dyeing technique, optimized concentration of dye material, optimized time for extraction and dyeing and optimized temperature for extraction and dyeing.

Colour fastness Tests of dyed samples:

As per the results of evaluation by judges the best shades out of 13 shades were selected. Finally 9 different shades of yellow were included in the final range of shades (table- A). Further Tests of the final range of shades, for colour fastness to light and washing were done at the Department of Textile Technology, IIT Delhi.

RESULTS AND DISCUSSION:

The rhizomes of the perennial turmeric are the source of colour. It is cultivated in almost all the parts of India Curcumin is the prime principal constituent of yellow dye, along with other constituents like monodesmethoxycurcumin and bidesmethoxycurcumin, which also contributes fewer amounts of pigment and flavour (GULRAJANI M L).Under experimental trials, different methodologies were tried for the extraction of colour and dyeing of wool. Figures and tables I to IV show the results of the experiments.

Figure I & table I show the results of colourimetric analysis (at 380 nm) and visual analysis at various parameters explained earlier. As per the results technique one was selected as appropriate for turmeric dye as this produced much bright hue as compared to dyeing technique II.

Fig II & table II reveal the results of optimization of concentration of Turmeric dye. According to results 2gms of Turmeric per 100 ml of water, for dyeing 10 gm of wool was found as optimum concentration. Anshu (1987) has recommended that 2 gm of dye is required per gm of wool to obtain optimum colour from natural dye Turmeric. This is a bit different from findings of the present study i.e. 2 gm of Turmeric dye is required to dye 10 gm of wool.


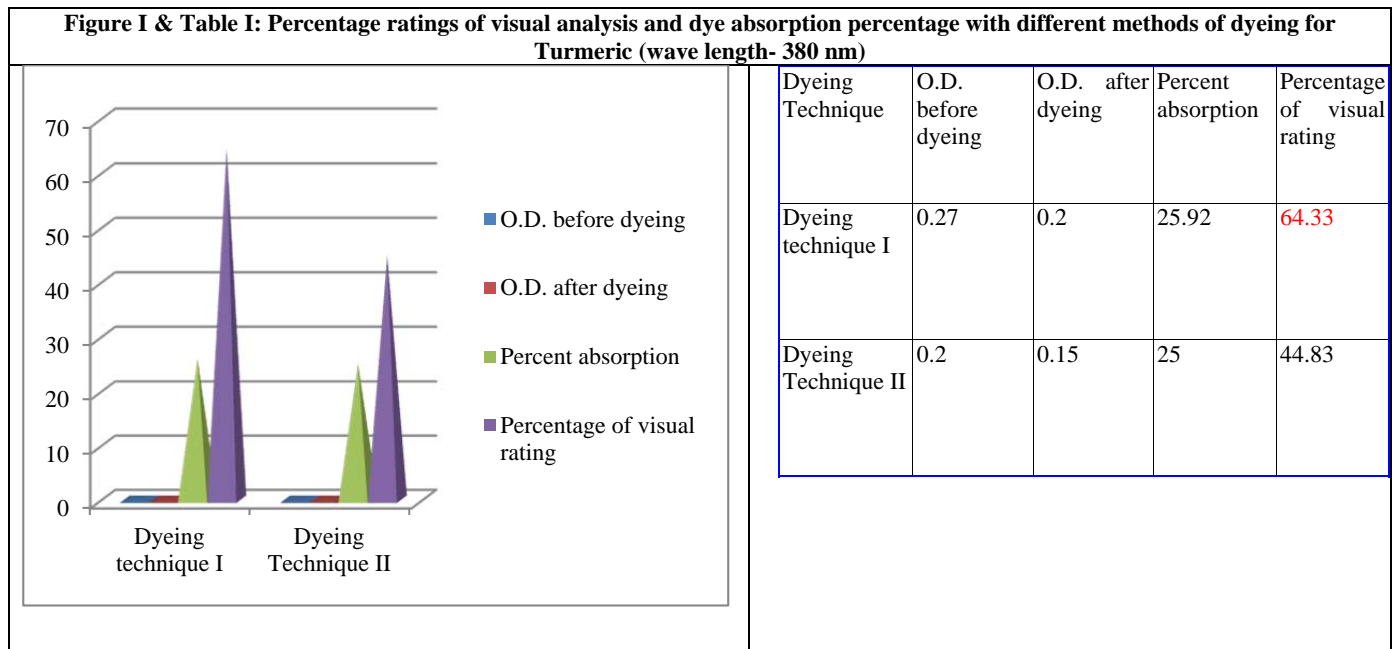


Figure II & Table II : Percentage ratings of visual analysis and dye absorption percentage (at 380 nm) with different concentrations of dye for Turmeric

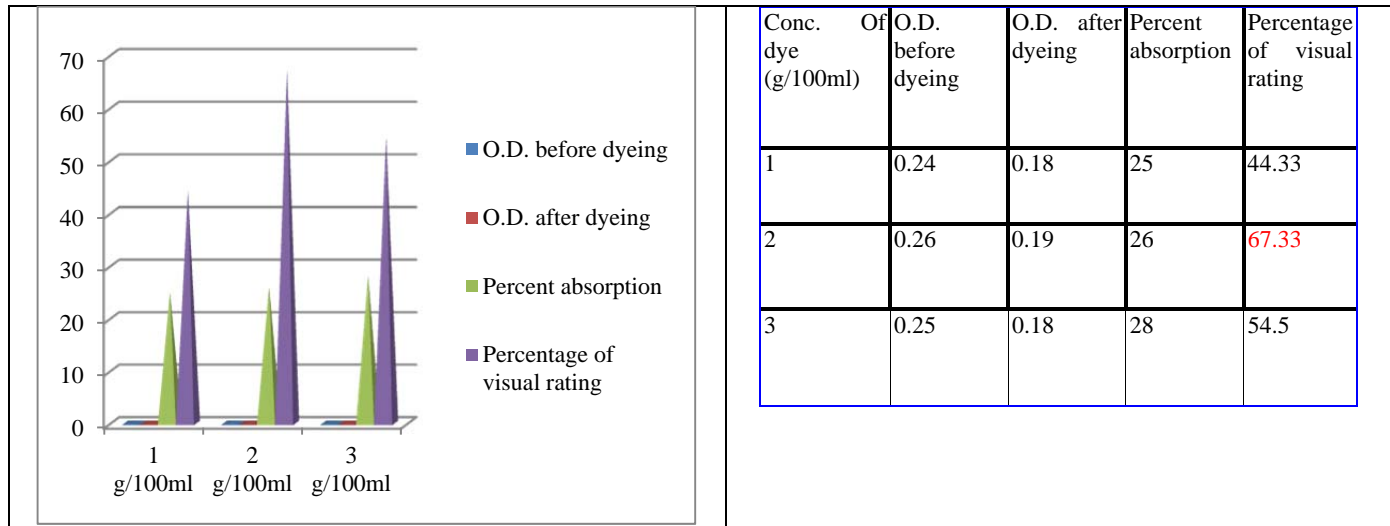

This variation in findings may be due to natural variation in sources of dyes used and also wool used. It's a well known fact that properties of natural products vary too much because of variation in environment and nourishment of the source used. Results of colorimetric analysis and visual analysis (to optimize the time for dyeing) show that 60 min. dyeing time is appropriate for Turmeric. Maximum dye absorption was found at 60 min. duration (Table III and Figure III). Results show that dyeing beyond 60 min. makes the hue dull. The decrease in colour strength for 120 minutes of dyeing may be attributed to desorption of dye molecules as a consequence of over dyeing (Nagia F A & El- Mohamedi, 2007). Cavendish (1978) has reported that extraction time of natural dyes varies from 20 to 120 minutes. The observations of the present study fall within this range. Fig IV and table IV show that 40^oc temperature provides the best results for dyeing with Turmeric. Temperature beyond that made the hue more Grayish. The Dye absorption was also found maximum at 40^oc. The results indicate that high temperature should be avoided for dyeing with turmeric if a bright hue is required. However Saima Umbreen et.al report that maximum colour strength is obtained at 90^oc but dyeing is not uniform. (Umbreen Saima, 2008). This variation in findings may be due to natural variation in sources of dyes used and also procedures used. Even slight variations in environment, water, soil etc may cause variation in crops and products.

Table B shows the various shades achieved through different dyeing procedures during optimization process. The **sample #7 Corn Silk** has been dyed with all optimized parameters (Dyeing technique I, conc. of dye 2%, temperature 40^oc, Dyeing time-60 min.). It also shows the results of color fastness tests to Light and Washing. Most of the shades exhibited poor to fair fastness to light. The samples were found to be affected by light rapidly. The shades processed at high temperature exhibited a bit better colour fastness to light. For shades done at high temperature a grade of 3 (fair) was observed. Over all the range of light fastness grades were between 2 to 3 (poor to

Figure III & Table III : Percentage ratings of visual analysis and dye absorption percentage (at 380 nm) at different time durations for Turmeric dye


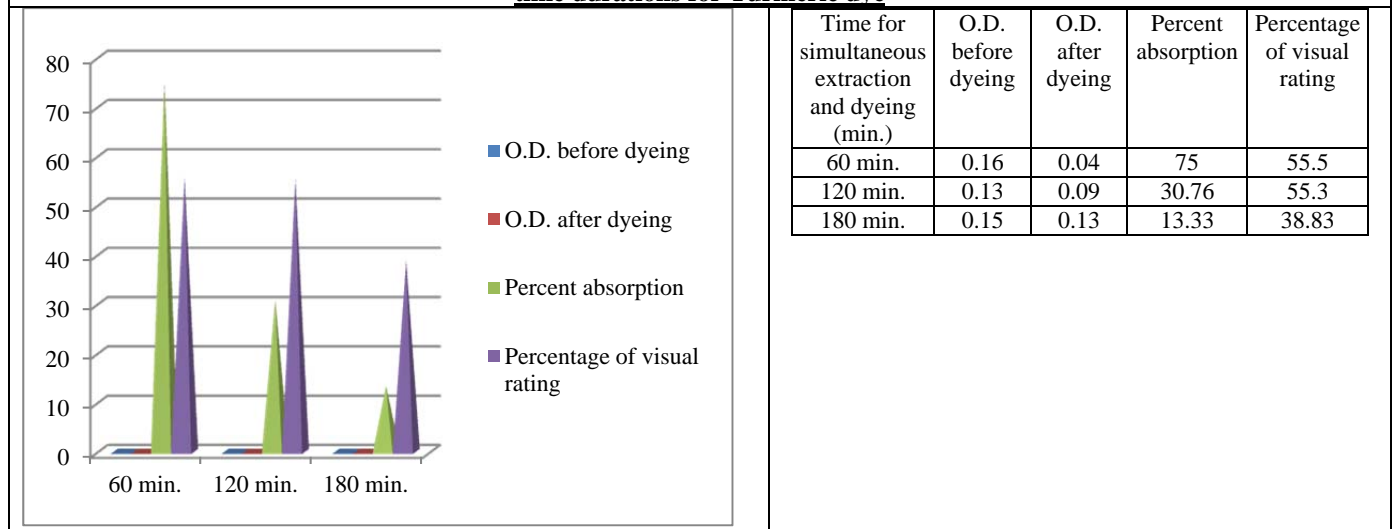


Figure IV & Table IV: Percentage ratings of visual analysis and dye absorption percentage (at 380 nm) at different temperatures for Turmeric dye








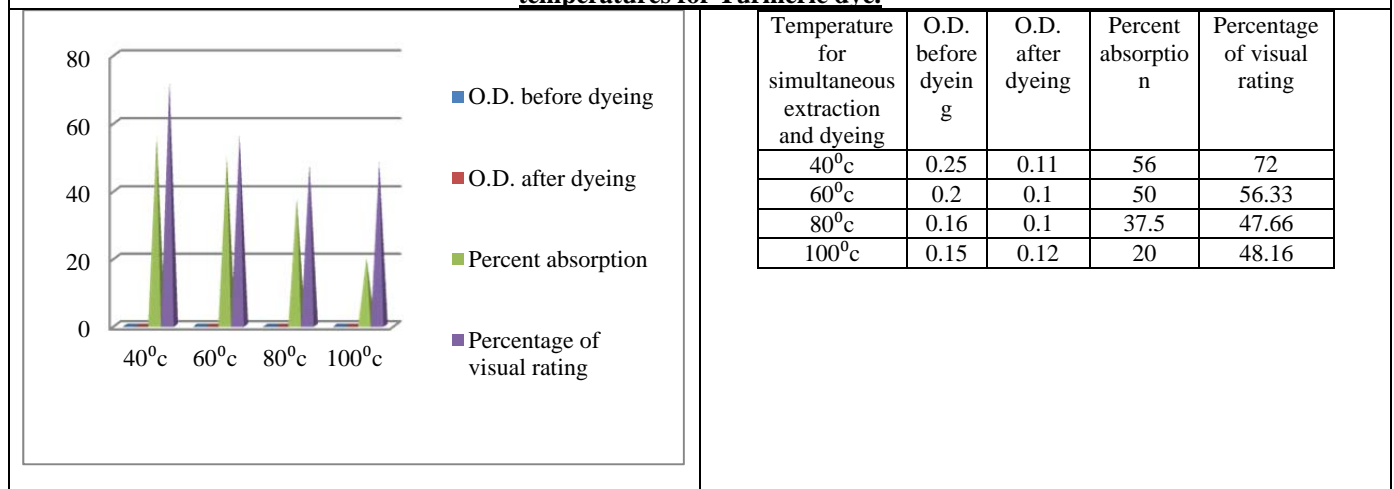



fair). Samples showed better grades for colour fastness to washing (3- 5). Best grades were observed for Flaxen, Ripe Hay and Pale flaxen (4- 5) good to excellent for change in colour, good for staining on cotton (4) & good to excellent for staining on wool. Lowest ratings were observed for Lion Yellow. Rest of the shades got a satisfactory rating of good to excellent (4-5) for colour change and staining as well.

CONCLUSION:

There are three basic needs that a man possesses food, clothing, and shelter. The global textile and clothing industry is bound to be huge, as it fulfills the second basic requirement of man. It is worth \$480 billion at present and is expected to reach \$700 billion, shortly, but the sad fact is that the human greed to look appealing and wear glamorous clothes has ended up causing harm to the environment. This is then led to returning to traditional and more natural way of life (patel BH). The present study was aimed at developing 100% natural bright yellow colour for dyeing of wool without the use of any synthetic stuffs as mordants. A number of shades were developed with good to excellent washing fastness, through variations in dyeing conditions only. No synthetic chemical was used at any stage. A series of experiments were conducted to compare and analyze the results two different procedures of dyeing, by means of colorimetric analysis and visually by trained subject experts. The water soluble yellow dye from turmeric rhizomes (Curcumin) is very fugitive in nature. The hue becomes dull with exposure to time and temperature. The conventional aqueous extraction procedure involves a time gap between extraction of dye and actual dyeing of the substrate. This exposure to time gap makes the dye dull and unappealing. Simultaneous extraction and dyeing method was

found to yield bright hues of yellow dye as decided by colorimetric tests and visual analysis. The colours are brighter and appealing as the dye is absorbed by the substrate as soon it is released in water bath. The size of the dye bag also plays an important role about the results of dyeing as revealed by various experiments. The dye bag should be only 1/3rd filled to achieve the best results. Observations proved that less temperature and reduced time of dyeing give better results in terms of colour appeal. Whereas analysis of the shade cards after a prolonged time gap of 23 years shows that the high temperature and prolonged dyeing time produced more durable and subdued colours. Thus any of the dyeing technique can be used as per the requirement of end product. There is a lot of scope to use the Turmeric dye for obtaining numerous colour shades, using safe eco-friendly textile dyeing.

SN	Sample		Ratings for Colour fastness to light	Colour fastness to washing		
				Ratings for colour change	Ratings for staining on cotton	Ratings for staining on wool
I.	Pale Dijon		2- 3	4	3-4	4
II.	Flaxen		3	5	4	4-5
III.	Dijon		2	4	3	4
IV.	Dandelion Yellow		3	4-5	3-4	4
V.	Straw Yellow		3	3-4	5	3-4
VI.	Lion Yellow		2	3	2	4
VII.	Corn Silk		2	4	3-4	4
VIII.	Ripe Hay		3	5	4	4-5
IX.	Pale Flaxen		2-3	4-5	4	4-5

ACKNOWLEDGEMENT

The Author is thankful to following agencies for their support extended during course of study; Department of Clothing and Textiles, G B Pant University of Agriculture and Technology, Pantnagar, Uttarakhand. Department of Chemistry, G B Pant University of Agriculture and Technology, Pantnagar, Uttarakhand. Department of Post Harvest Tech., G B Pant University of Agriculture and Technology, Pantnagar, Uttarakhand. Department of Textile Technology, I.I.T., New Delhi. Alps Industries Ltd, Mohan Nagar, Ghaziabad, UP

BIBLIOGRAPHY

- [1] Anshu, (1987). Development of dyeing process for wool with natural dyes Henna and Turmeric. Thesis, M Sc(Clothing and Textiles), GBPUA&T, Pantnagar.62P.
- [2] Gulrajani m l, g. d. (1993). Natural dyes and their application to textiles. new delhi: i i t delhi.
- [3] Gulrajani M L, G. D. (Jan 1992). Some studies on yellow natural dyes; Part I. *Indian Textile Journal* , 50- 56.
- [4] Neelam Pruthi, G. D. (2007). Dyeing of Silk with Barberry bark. *Natural product Radiance* , 40- 44.
- [5] Patel BH, A. B. (2006). improving the environmental and economic aspects of cotton dyeing using vegetable dyes. *colourage* , 6:49 - 58.
- [6] Paul R, J. M. (1996). Classification Extraction and fastness properties. *textile Dyer and printer* 31 (6 ,)16- 24.
- [7] Umrao Singh and Others (1983). Dictionary of Economic plants in India. Indian council of Agricultural research, New delhi, 51- 52

- [8] Sachan K & Kapoor VP (April 2007) Optimization of extraction and dyeing conditions for traditional turmeric dye. Indian Journal of Traditional Knowledge, Vol6(2), 270 -278
- [9] ISI Hand Book of Textile Testing, (1982) Indian Standards institution, New Delhi, 538- 539, 571- 572
- [10] Umbreen S, Ali S, Hussain T & Nawaz R (2008).Dyeing properties of natural dyes extracted from Turmeric and their comparison with reactive dyeing. Research Journal of Textile and Apparel Vol 12 no 4
- [11] Abrahart e n, dyes and their intermediates, London, oxford kergamon, 1977.
- [12] Compton's pictured encyclopedia, Chicago, f e, Compton and company, 1955.